

The order of the metal to superconductor transition

S. Mo,^{1,*} J. Hove,^{1,†} and A. Sudbø^{1,2,‡}

¹*Department of Physics
Norwegian University of Science and Technology,
N-7491 Trondheim, Norway*

²*Institut für Theoretische Physik
Freie Universität Berlin
Arnimallee 15, D-14195 Berlin, Germany*

(Dated: February 1, 2008)

We present results from large-scale Monte Carlo simulations on the full Ginzburg-Landau (GL) model, including fluctuations in the amplitude and the phase of the matter-field, as well as fluctuations of the non-compact gauge-field of the theory. From this we obtain a precise critical value of the GL parameter κ_{tri} separating a first order metal to superconductor transition from a second order one, $\kappa_{\text{tri}} = (0.76 \pm 0.04)/\sqrt{2}$. This agrees surprisingly well with earlier analytical results based on a disorder theory of the superconductor to metal transition, where the value $\kappa_{\text{tri}} = 0.798/\sqrt{2}$ was obtained. To achieve this, we have done careful infinite volume and continuum limit extrapolations. In addition we offer a novel interpretation of κ_{tri} , namely that it is also the value separating type-I and type-II behaviour.

PACS numbers: 74.55.+h, 74.60.-w, 74.20.De, 74.25.Dw

I. INTRODUCTION

The character of the metal to superconductor transition is an important and long-standing problem in condensed matter physics. The critical properties of a superconductor may be investigated at the phenomenological level by the Ginzburg-Landau (GL) model of a complex scalar matter field ϕ coupled to a fluctuating mass-less gauge-field $\mathbf{A}$. The GL model in d -dimensions is defined by the functional integral

$$Z = \int \mathcal{D}A_i \mathcal{D}\phi \exp(-S(A_i, \phi))$$

$$S = \int d^d x \left[\frac{1}{4} F_{ij}^2 + |D_i \phi|^2 + m^2 |\phi|^2 + \lambda |\phi|^4 \right] \quad (1)$$

where $F_{ij} = \partial_i A_j - \partial_j A_i$, $D_i = \partial_i + iqA_i$, q is the charge coupling the condensate matter field to the fluctuating gauge-field, λ is a self-coupling, and m^2 is a mass parameter which changes sign at the mean field critical temperature. This model is also used to describe a great number of other phenomena in Nature, including such widely separated phenomena as the Higgs mechanism in particle physics,¹ phase transitions in liquid crystals,^{2,3} crystal melting,⁴ the quantum Hall effect,^{5,6} and it is also used as an effective field theory describing phase transitions in the early Universe.⁷

The GL model may conveniently be formulated in terms of two dimensionless parameters $y = m^2/q^4$ and $x = \lambda/q^2$ when all dimensionful quantities are expressed in powers of the scale q^2 . Here, y is temperature-like and drives the system through a phase transition, and $x = \kappa^2$ is the well known GL parameter. These parameters are related to the standard dimensionful textbook⁸

coefficients α, β of the GL model by

$$y = \frac{m^* c^2}{128 \pi^2 \alpha_s^2 k_B^2 T^2} \alpha, \quad x = \frac{1}{8 \pi \alpha_s \hbar c} \left(\frac{m^* c}{\hbar} \right)^2 \beta = \kappa^2 \quad (2)$$

where α_s is the fine structure constant³⁵ and m^* is an effective mass parameter.

At the mean-field level Eq. 1 reduces to the well known GL-equations and the model exhibits a second order phase transition when the temperature (or y) is varied through some critical value. In a seminal paper by Halperin, Lubensky and Ma⁹ it was shown that by ignoring spatial fluctuations in ϕ , and then integrating out the $\mathbf{A}$ field *exactly*, one gets a term $|\phi|^3$ in the effective ϕ action. Treating this action at the mean field level leads to the prediction of a first order transition in the charged model for any value of the charge, or equivalently for any value of the GL parameter. The first order character of the transition is most strongly pronounced for large values of the charge (small κ), but even then it is very weak. For $\kappa \ll 1$ (type-I) the neglect of spatial variation in the matter field ϕ is a reasonable approximation, whereas for $\kappa \gtrsim 1$ (type-II) fluctuations in ϕ must be taken into account. By doing a one-loop RG calculation using ε -expansion it was shown⁹ that no stable infrared fixed point could exist unless the number N of components of the order-parameter was artificially extended to $N > N_c = 365$, far beyond the physically relevant case of $N = 2$. Consequently, the conclusion was that gauge field fluctuations change the order of the phase transition to first order *irrespective* of the value of κ .

These predictions were difficult to test experimentally on superconductors since the predicted jump across the first order transition is very small in *physical* units, even if the *effective* theory in Eq. 1 has a strong first order transition. See e.g. Appendix A in Ref. 10. For conven-

tional superconductors the critical region where mean-field behavior breaks down is extremely narrow, consequently it is very difficult to distinguish a small finite jump from continuous behavior. However, there exists an isomorphism between the phase transition in superconductors and the smectic-A to nematic transition in liquid crystals.¹¹ On the latter systems experiments can be carried out in the critical regime,¹² and second order phase transitions are found. This contradicts the ϵ -expansion argument above, and presumably indicates a breakdown of the expansion for this gauge-field theory, since $\epsilon = 4 - d = 1$.

In Ref. 13 it was shown, using duality arguments and Monte Carlo simulations, that the GL model should have a second order transition for large κ . However, what remains true is that deep in the type-I regime, the transition *is* first order. There should therefore be a tricritical point $\kappa = \kappa_{\text{tri}}$ where the transition changes order.

A first estimate for κ_{tri} was obtained by Kleinert in Refs. 14,15 by developing a disorder theory formulation from which he calculated the value

$$\kappa_{\text{tri}} = \frac{3\sqrt{3}}{2\pi} \sqrt{1 - \frac{4}{9} \left(\frac{\pi}{3}\right)^4} \approx \frac{0.798}{\sqrt{2}}$$

analytically³⁶. Subsequently¹⁶ this picture of a tricritical point separating first and second order transitions was given further support by Monte-Carlo simulations, and moreover an attempt was even made to determine κ_{tri} , giving $\kappa_{\text{tri}} \simeq 0.4/\sqrt{2}$. However, the problem turns out to be extremely demanding even by present day supercomputing standards, and not too much emphasis can be put on the *precise numerical value* obtained in this early attempt. To our knowledge, this is the most recent attempt to find a precise value for κ_{tri} numerically, although large-scale simulations have been performed much more recently for $\kappa^2 = 0.0463$ and $\kappa^2 = 2$, giving first order and continuous transitions, respectively.^{10,17}

The one-loop ϵ -expansion result of Halperin *et al.*⁹ has subsequently been improved to two-loop order,¹⁸ drastically reducing the value of N_c to 32, but still $N_c \gg 2$. Eventually, an infrared stable fixed point was found even for the physical case $N = 2$ by combining two-loop perturbative results with Padé-Borel resummation techniques.¹⁹ From this latter work one can also get an estimate of the critical κ from $\kappa^* = \sqrt{u^*/6f^*} \approx 0.62/\sqrt{2}$. Since Padé-Borel techniques are rather uncontrolled, only simulations can tell if such a resummation is allowed here.

From the above we can conclude that a tricritical κ , separating first and second order transitions *exists*, however a *precise value* remains to be determined..

We would also like to mention the distinction between type-I and type-II superconductors, which is related to the response to an external magnetic field. When an external field is increased beyond a critical field H_c it enters a type-I superconductor, and superconductivity is destroyed. For type-II superconductors the magnetic field enters as a *flux line lattice* when $H > H_{c1}$, and superconductivity is still present in this mixed state. At

the mean-field level type-I and type-II superconductors are differentiated by $\kappa = 1/\sqrt{2}$. However there is a priori no reason to assume that this numerical value is robust against fluctuation effects, and we will argue that the critical κ separating first and second order phase transitions coincides with the κ separating type-I and type-II superconductors at y_c .

II. THE ORDER OF THE TRANSITION

The model in Eq. 1 has a phase transition for $y = y_c$. For $y < y_c$ the system is in its superconducting (broken) phase while for $y > y_c$ it is in the normal (symmetric) phase. Note that here, broken/symmetric does not refer to a breakdown of the local gauge symmetry present in Eq. 1. Elitzur's theorem²⁰ states that a local symmetry can never be spontaneously broken and therefore no local order parameter (in general any non-gauge invariant order parameter) can exist. On the other hand, one can explicitly break the gauge symmetry by a gauge-fixing, thereby facilitating a meaningful definition of a local order parameter. This should nonetheless be chosen in a formally gauge-invariant manner to get gauge-independent results. In our simulations, we have chosen not to fix the gauge³⁷. In this case a phase transition must be found either by using *non-local*^{17,21} order parameters or by looking for non-analytic behavior in local quantities,¹⁰ as we have done. E.g. the quantity $\langle |\psi|^2 \rangle$ will have a jump at a first order transition, but it will not disappear in the symmetric phase as a proper order parameter should. At a second order transition there will be no jump, but the susceptibility $\chi_{|\psi|^2}$ will still have a peak.

In principle, we could therefore decide the order by looking for a jump in some local quantity as $\langle |\psi|^2 \rangle$, but in finite systems the discontinuity will be rounded. In our case this is particularly problematic since the first order transitions are very weak, giving small jumps, even in infinite systems. At a first order transition ordered and disordered phases coexist and have the same free energy. In a finite system there will therefore be oscillations between the different phases. Because of the surface energy between the two pure states the probability of finding the system in an intermediate mixed state is lower than for either of the pure states, and histograms of an arbitrary observable will show a pronounced double peak structure. This is in contrast to a second order transition where the diverging correlation length forbids coexistence since the whole system is correlated. The histograms then have a single peak. Typical histograms are shown in Fig. 2.

Thus, when these histograms have a double peak structure which becomes more pronounced when the system size increases, the transition is first order, otherwise not.²²

More precisely, we have the following scaling for the difference in free energy between the mixed and pure

phases for sufficiently large $L > L_{\text{scaling}}$

$$\Delta F(L) = \ln P(X, L)_{\text{max}} - \ln P(X, L)_{\text{min}} \sim L^{d-1}, \quad (3)$$

where $P(X, L)$ is the probability for a given observable X in a system of size L^d , and L^{d-1} is the cross-sectional area between the ordered and the disordered phase. Near the tricritical value of κ such scaling is difficult to achieve since we are interested in the limit of vanishingly weak first order transitions. Consequently, a very large L is required in order to observe proper scaling. Only for quite strong first order transitions have we been able to observe proper scaling as predicted by Eq. 3, however we have generally taken a monotonous increase in $\Delta F(L)$ with system size as a signature of a first order phase transition. For the weakest first order transitions $\Delta F(L)$ will typically decrease for small L and then start to increase. It is therefore important to observe monotonic behavior through several system sizes before a conclusion can be drawn from the histograms³⁸.

III. PHASE DIAGRAM

We are searching for the point in the (x, y) plane where a first order and a second order line meet, i.e. according to the rather loose definition³⁹ of Lawrie and Sarbach²³ we are looking for a *tricritical point*. At a tricritical point *two* coupling constants must be fine-tuned to nontrivial values, and consequently a tricritical theory can be described with the mean-field free energy

$$f \approx |\nabla\psi|^2 + c_1(y - y_{\text{tri}})|\psi|^2 + c_2(x - x_{\text{tri}})|\psi|^4 + c_3|\psi|^6. \quad (4)$$

Right at the tricritical point the coefficients in front of both $|\psi|^2$ and $|\psi|^4$ vanish *simultaneously*. The upper critical dimension for this model is $d^* = 3$ and mean-field theory should be valid (up to logarithmic corrections). When approaching the tricritical point from the first order side, mean-field theory predicts that the jump $\Delta|\psi|^2$ will vanish as

$$\Delta|\psi|^2 \sim (x_{\text{tri}} - x). \quad (5)$$

We will make use of the above scaling in section VI to estimate x_{tri} . For further information about tricritical points, we refer to an extensive review by Lawrie and Sarbach.²³

In Fig. 1 we have *assumed* that the tricritical point separating first order and second order phase transitions coincides with the point separating type-I and type-II superconductivity. In principle the line of second order transitions could extend into the type-I region, with an intermediate state of type-I superconductivity with a second order phase transition to the normal state. This would be the case if the mean field value $\kappa_{\text{I/II}} = 1/\sqrt{2}$ was *not* renormalized by fluctuations. We have not focused on the aspect of type-I/II superconductivity in our

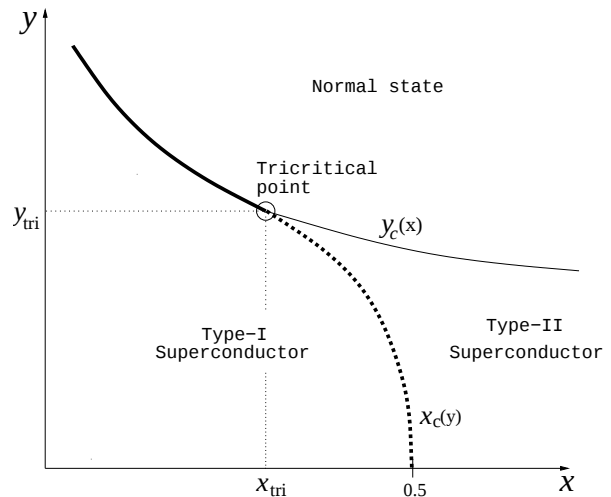


FIG. 1: A conjectured phase diagram in the (x, y) plane in the vicinity of the tricritical point. The thick solid line is a line of first order transitions separating type-I superconductivity and the normal (metallic) state, the thin solid line is a second order line separating type-II superconductivity from the normal (metallic) state. The dashed line separates type-I and type-II superconductivity. The dotted horizontal and vertical lines indicate the coordinates of the tricritical point $(x_{\text{tri}}, y_{\text{tri}}) \simeq (0.30, 0.03)$.

simulations, we will however argue that the overall structure of the phase diagram shown in Fig. 1 is correct in the vicinity of the tricritical point.

The microscopic difference between type-I and type-II superconductors lies in the sign of the effective vortex-vortex interaction. In $d = 3$ there exists a *dual* formulation of the GL-model which is given by a complex scalar matter-field ϕ coupled minimally to a massive gauge-field. This gauge-field can thus safely be integrated out to yield an effective *local* $|\phi|^4$ -theory, where the coefficient of the $|\phi|^4$ -term gives the effective vortex-vortex interaction. A positive such term signals vortex-repulsion, i.e. type-II behavior, while a negative term signals type-I behavior. *This vortex-vortex interaction term is proportional to $\kappa - \kappa_{\text{tri}}$ where κ_{tri} is indeed to be identified with our tricritical value of κ .*¹⁴ Using the dual formulation of the GL theory, it then becomes clear that κ_{tri} is at the same time the value that separates first order and second order behavior, *and* the value that separates attractive from repulsive effective vortex-vortex interactions, i.e. type-I from type-II behavior.

An independent argument for why the transition between the normal state and type-I superconductivity *must be first order*, is based on the geometrical properties of a vortex tangle: In a recent paper²⁴ we have calculated the fractal dimension of vortex loops, and found the scaling relation $\beta = \nu(d - D_H)/2$, where β is the order parameter exponent, ν is the correlation length exponent and D_H is the fractal dimension of the loops. If

we formally extend this relation to the first order regime, i.e. let $\beta \rightarrow 0^+$, we find that the fractal dimension of the vortex loops $D_H \rightarrow d$, i.e. the vortices collapse on themselves (filling space completely), rendering the transition discontinuous. This collapse is what we would expect from vortices interacting attractively (i.e. type-I), and by turning the argument above around we conclude that type-I superconductors must have a first order transition to the normal state.

We emphasize that the detailed *shape* of the line $x_c(y)$ remains to be determined. We have presented arguments above that it ends in the tricritical point $(x_{\text{tri}}, y_{\text{tri}})$. Moreover, deep in the broken regime, mean-field theory should apply. Consequently, we expect that the line $x_c(y)$ converges towards the mean field value $x_{\text{I/II}} = 1/2$ in the $y \rightarrow -\infty$ limit.

IV. LATTICE MODEL

To perform simulations on the model in Eq. 1 we define it on a numerical lattice of size $N \times N \times N$ with lattice constant a . The *physical* volume is then $V = L^3 = (Na)^3$. By introducing a lattice field given by

$$|\phi_{(\text{cont})}|^2 = \beta_H |\psi_{(\text{latt})}|^2 / 2a, \quad (6)$$

where β_H so far is an arbitrary constant, Eq. 1 takes the form

$$\begin{aligned} Z &= \int \mathcal{D}A_i \mathcal{D}\psi \exp(-S(A_i, \psi)) \\ S &= \beta_G \sum_{\vec{x}, i < j} \frac{1}{2} F_{ij}^2 - \beta_H \sum_{\vec{x}, i} \text{Re} \left(\psi^*(\vec{x}) U_i(\vec{x}) \psi(\vec{x} + \hat{i}) \right) \\ &\quad + \frac{\beta_H}{2} \left[6 + \frac{y}{\beta_G^2} \right] \sum_{\vec{x}} |\psi|^2 + \beta_R \sum_{\vec{x}} |\psi|^4 \end{aligned} \quad (7)$$

where we have defined $\alpha_i(\vec{x}) = aq A_i(\vec{x})$, $U_i(\vec{x}) = e^{i\alpha_i(\vec{x})}$, $\beta_G = 1/aq$, $F_{ij} = \alpha_i(\vec{x}) + \alpha_j(\vec{x} + \hat{i}) - \alpha_j(\vec{x}) - \alpha_i(\vec{x} + \hat{j})$, and $\beta_R = x\beta_H^2/4\beta_G$. F_{ij} is essentially a lattice curl of the fluctuating gauge-field, and $aq = aq^2$ is a dimensionless lattice constant. To obtain correct continuum limit results, we will ultimately be interested in the limit $a_q \rightarrow 0$. It is furthermore possible to select a value of β_H such that the action can be written on the form

$$\begin{aligned} S &= \beta_G \sum_{\vec{x}, i < j} \frac{1}{2} F_{ij}^2 - \beta_H \sum_{\vec{x}, i} \text{Re} \left(\psi^*(\vec{x}) U_i(\vec{x}) \psi(\vec{x} + \hat{i}) \right) \\ &\quad + \sum_{\vec{x}} |\psi|^2 + \beta_R \sum_{\vec{x}} [|\psi|^2 - 1]^2. \end{aligned} \quad (8)$$

This is achieved provided β_H satisfies the relation $(\beta_H/2)[6 + y/\beta_G^2] + 2\beta_R = 1$.

The amplitude and gauge-invariant phase difference $\Delta = \arg(\psi^*(\vec{x}) U_i(\vec{x}) \psi(\vec{x} + \hat{i}))$ are coupled through the second term in Eq. 8. The ordered state is characterized by $\cos \Delta \lesssim 1$ and $|\psi|$ close to the minimum in the potential energy, whereas in the disordered state $\cos \Delta \approx 0$.

In the disordered state the amplitude behavior is determined by x ; for small x the coupling to Δ dominates and $|\psi|$ deviates significantly from the minimum in the potential, whereas for large x amplitude fluctuations are suppressed.

Given the fact that the theory in Eq. 1 is a continuum theory, one has to perform an ultraviolet (short-distance) renormalization, and thus $m^2 = m^2(q^2)$ has to be interpreted as a renormalized mass parameter at a given scale q^2 within a given renormalization scheme, e.g. the minimal subtraction ($\overline{MS}$) scheme. Since this continuum theory should represent the $a \rightarrow 0$ limit of the lattice theory in Eq. 8, the parameter y must be varied when a is being varied. In our case the leading terms in a can be obtained by requiring that some physical correlator calculated in both lattice and continuum perturbation theory should coincide. Thus we have to make the substitution^{25,26}

$$\begin{aligned} y &\rightarrow y - \frac{3.1759115(1+2x)}{2\pi} \beta_G \\ &\quad - \frac{(-4+8x-8x^2)(\ln(6\beta_G) + 0.09) - 1.1 + 4.6x}{16\pi^2} \\ &\quad + \mathcal{O}(1/\beta_G) \end{aligned} \quad (9)$$

In addition, the continuum and lattice condensate matter fields are related by

$$\begin{aligned} \frac{\langle \phi^* \phi \rangle_{\text{cont}}}{q^2} &= \frac{\beta_H \beta_G}{2} \langle \psi^* \psi \rangle_{\text{latt}} \\ &\quad - \frac{3.175911\beta_G}{4\pi} - \frac{\log(6\beta_G) + 0.668}{8\pi^2} + \mathcal{O}(1/\beta_G). \end{aligned} \quad (10)$$

In Eq. 10 the first term comes from Eq. 6, while the second and third terms are linear and logarithmic divergences due to renormalization.

Note that the complicated counterterms in Eq. 9 merely affect the *value* of y_c separating the normal from the superconducting state for a given x , not the overall *structure* of the phase-diagram. The divergences in Eq. 10 in the continuum limit are constants that cancel when the jump in $\langle \phi^* \phi \rangle$ across a first order phase transition is calculated.

V. DETAILS OF SIMULATIONS

In order to use Eq. 8 to study the continuum theory of Eq. 1, it is necessary to carefully take two limits separately. First, the infinite volume limit $L \rightarrow \infty$ is taken, thereafter the continuum limit $a \rightarrow 0$. For reliable results one should have $a \ll \xi \ll L$, where ξ is a typical correlation length for the problem. In statistical physics, the continuum limit is usually not considered, either because the models are inherently *lattice models*, or the models are studied around a second order critical point where there exists at least one diverging length scale. Under such circumstances the short length-scale properties, like

TABLE I: The lattice sizes N^3 used for each (a_q, x) -pair. For each lattice size typically between three and eight y -values were used. The symbols are defined by:

- Not simulated
- ★ Simulated
- Simulated and results shown in Fig. 2.

a_q	x	N									
		8	12	16	20	24	32	40	48	64	96
5.0 ^a	0.10	★	○	○	○	○	○	○	○	○	○
	0.15	★	★	★	★	★	★	○	○	○	○
	0.16	★	★	★	●	●	●	○	○	○	○
	0.17, 0.18, 0.19	★	★	●	○	●	●	●	○	○	○
2.0	0.10	★	★	○	○	○	○	○	○	○	○
	0.15	★	★	★	○	○	○	○	○	○	○
	0.20	★	★	★	○	★	★	★	○	○	○
	0.22	○	○	●	○	●	●	●	○	○	○
	0.23, 0.24, 0.25	○	○	●	○	●	●	●	○	○	○
1.0	0.08	★	★	★	○	○	○	○	○	○	○
	0.10	★	★	★	★	○	○	○	○	○	○
	0.12, 0.13, 0.14	★	★	★	○	★	★	★	○	○	○
	0.15, 0.16, 0.17	○	★	★	★	★	★	★	○	○	○
	0.18, 0.20	★	★	★	○	★	★	★	★	○	○
	0.22	★	★	★	○	★	★	★	★	○	○
	0.24, 0.25, 0.26, 0.27	★	★	●	○	●	●	●	●	○	○
	0.30	★	★	★	○	★	★	★	★	○	○
	0.50	○	○	★	★	★	★	★	○	○	○
0.5	0.16	○	○	○	○	●	●	●	●	○	○
	0.20, 0.24	○	○	○	○	●	●	●	●	●	○
	0.26, 0.28	○	○	○	○	○	○	○	○	○	○
	0.30	○	○	○	○	○	○	○	○	○	○

^aIn Ref. 16 the lattice spacing corresponds to $a_q = 5.0$. The system sizes used were 9^3 and 15^3 .

the lattice constant, are rendered irrelevant when studying universal properties. On the other hand, if one wants to study non-universal properties (such as critical coupling constants) or first order transitions without a diverging length scale, details of the system even on the shortest length scales have to be correctly taken into account in order to give reliable results.

The Monte-Carlo simulations are performed on Eq. 8, updating phases, amplitudes⁴⁰, and gauge-fields. We have used periodic boundary conditions and non-compact gauge-fields without any gauge fixing. To reduce autocorrelation times we have added global updating of the amplitude and overrelaxation of the scalar field^{27,28} such that one sweep consists of: (1) conventional local Metropolis updates for phase, amplitude and gauge field, (2) global radial update by multiplying the amplitude uniformly with a common factor (acceptance according to Metropolis dynamics) and (3) 2-3 overrelaxation “sweeps” updating both the amplitude and the phase of the scalar field. The acceptance ratio in the Metropolis steps is kept between 60-70% as long as possible by adaptively adjusting the maximum allowed changes in the fields. For further details of the technical aspects of the simulations, see Refs. 27,28.

We have performed simulations for the parameters in Table I. The simulations have been done in a hierarchical manner: For a given x we have first kept a_q and N fixed, and simulated on typically three to eight y values. These runs have been combined with Ferrenberg-Swendsen^{29,30} reweighting techniques, and a (pseudo)critical y has been

located by requiring that the reweighted histograms have two equally high⁴¹ peaks. Then the system size has been increased to access the *infinite volume limit*, and finally we have varied a_q to determine the *continuum limit*. At the transition the number of sweeps was chosen so that the system oscillated back and forth between the ordered and disordered state about ten times. Depending on system size and x -value (i.e. the *strength* of the first order transition) this resulted in about 10^5 to 10^6 sweeps. All computations were performed on an SGI Origin 3800 at the Norwegian High Performance Computing Center, using up to 32 nodes in parallel for the largest systems. A total of about $5 \cdot 10^4$ CPU hours were used, corresponding to $\simeq 1.5 \cdot 10^{17}$ floating point operations.

VI. RESULTS

To find $x_{\text{tri}} = \kappa_{\text{tri}}^2$ our strategy has been to start at $x \ll x_{\text{tri}}$ where the transition is clearly first order, and then slowly increase x into the problematic tricritical area where $x \lesssim x_{\text{tri}}$. During the simulations we have sampled the lattice amplitude

$$\overline{|\psi|^2} = \frac{1}{N^3} \sum_{\vec{x}} |\psi(\vec{x})|^2 \quad (11)$$

and histograms of this quantity constitute the raw data for most of the subsequent analysis⁴². The connection between continuum and lattice condensates is given by Eq. 10.

Histograms reweighted to the critical y -value are shown in Fig. 2. We have used two different methods to find $x_{\text{tri}}(a_q)$ from the histograms, and finally at the end of this section we have extrapolated these values to $a_q = 0$ to find the continuum limit.

A. Extrapolation of $\Delta \overline{|\psi|^2}$ to zero

The distance between the peaks of a histogram gives $\Delta \overline{|\psi|^2}(N)$, and by computing this for several different system sizes one can compute the infinite volume limit $\lim_{N \rightarrow \infty} \Delta \overline{|\psi|^2}$ of the discontinuity at the transition. Then one can (in principle) extrapolate to larger x and find the value x_{tri} where the discontinuity disappears. Results for $\lim_{N \rightarrow \infty} \Delta \overline{|\psi|^2}$ as a function of x are shown in Fig. 3.

For small x the curves in Fig. 3 show a distinct positive curvature, but when approaching x_{tri} we find that $\Delta \overline{|\psi|^2}$ vanishes as $\propto (x_{\text{tri}} - x)$, in accordance with mean-field theory, Eq. 5. Also in the original attempt to locate x_{tri} with Monte Carlo simulations¹⁶ this extrapolation was done, however the extrapolation was done starting from quite small x values, and the resulting x_{tri} was much smaller than the one we calculate.

The extrapolated results for x_{tri} are shown in Table II. The values found should provide a reasonable upper limit

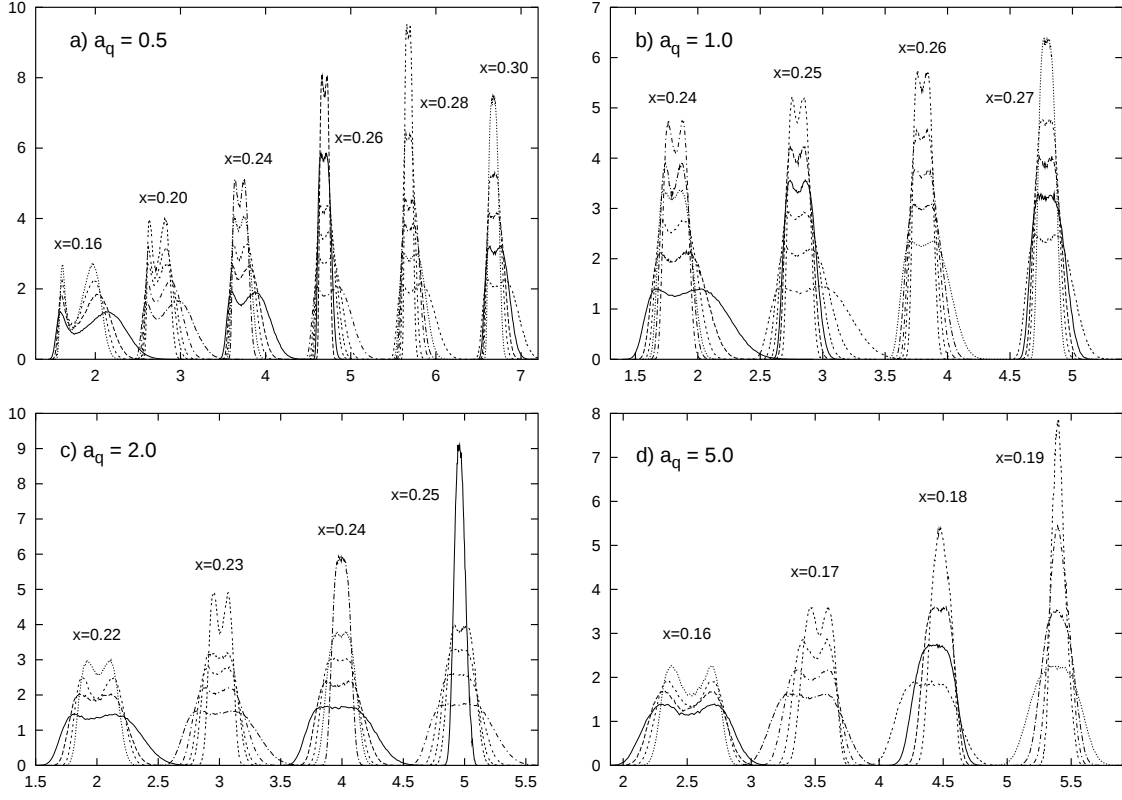


FIG. 2: Normalized histograms $P(\overline{|\psi|^2})$ as a function of $\overline{|\psi|^2}$ for a) $a_q = 0.5$, b) $a_q = 1.0$, c) $a_q = 2.0$, d) $a_q = 5.0$. For each lattice spacing the histograms for the smallest x are correctly placed horizontally. For larger x they are offset horizontally in steps of 1 for clarity. For system sizes see Table I.

TABLE II: x_{tri} found from extrapolation of $\lim_{N \rightarrow \infty} \Delta \overline{|\psi|^2}$ to zero and finite size scaling of $\Delta F(N)$.

a_q	x_{tri} (from $\Delta \overline{ \psi ^2}$)	x_{tri} (from $\Delta F(N)$)
5.0	0.174 ± 0.002	0.175 ± 0.005
2.0	0.246 ± 0.002	0.235 ± 0.005
1.0	0.286 ± 0.010	0.260 ± 0.010
0.5	0.294 ± 0.005	0.280 ± 0.020

for $x_{\text{tri}}(a_q)$.

B. Finite size scaling of $\Delta F(N)$

It is also possible to study the *height* of the peaks in the histograms $[P(\overline{|\psi|^2})_{\text{max}}]$ relative to the minimum between them $[P(\overline{|\psi|^2})_{\text{min}}]$. This constitutes the best method of determining whether a transition is first order or not, but one cannot extrapolate to find x_{tri} . In Fig. 4 we show some typical results for $\Delta F(N) = \ln P_{\text{max}} - \ln P_{\text{min}}$ as function of system size N for $a_q = 0.5$.

For $x = 0.16$ we clearly see the scaling $\Delta F(N) \propto N^2$ for $N \gtrsim 40$. This is expected since the histograms in Fig. 2 show a very pronounced double peak structure.

For larger x this becomes less clear. Our estimates of x_{tri} for the different lattice constants are given in Table II. The results are consistently somewhat below those found with method A and give a reasonable lower limit for x_{tri} .

C. Other methods

Finite-size scaling of the maximum in susceptibilities of the quantities $|\psi|^2$ and $\overline{L}$ gives results that are consistent with the above conclusions.

$$\chi_S = N^d \left(\langle S^2 \rangle - \langle S \rangle^2 \right) \sim N^\sigma, \quad S \in \{\overline{|\psi|^2}, \overline{L}\} \quad (12)$$

where $\sigma = d(< d)$ for first(second) order transitions. However, these results are more ambiguous than those from the histograms, and we have therefore chosen to work mainly with the histograms.

D. Final result for κ_{tri}

It is clear that it becomes increasingly difficult to obtain good estimates of $\kappa_{\text{tri}}(a_q)$ when the lattice constant is reduced. This is easy to understand since the *physical* volume $(Na_q)^3$ will be drastically reduced for the

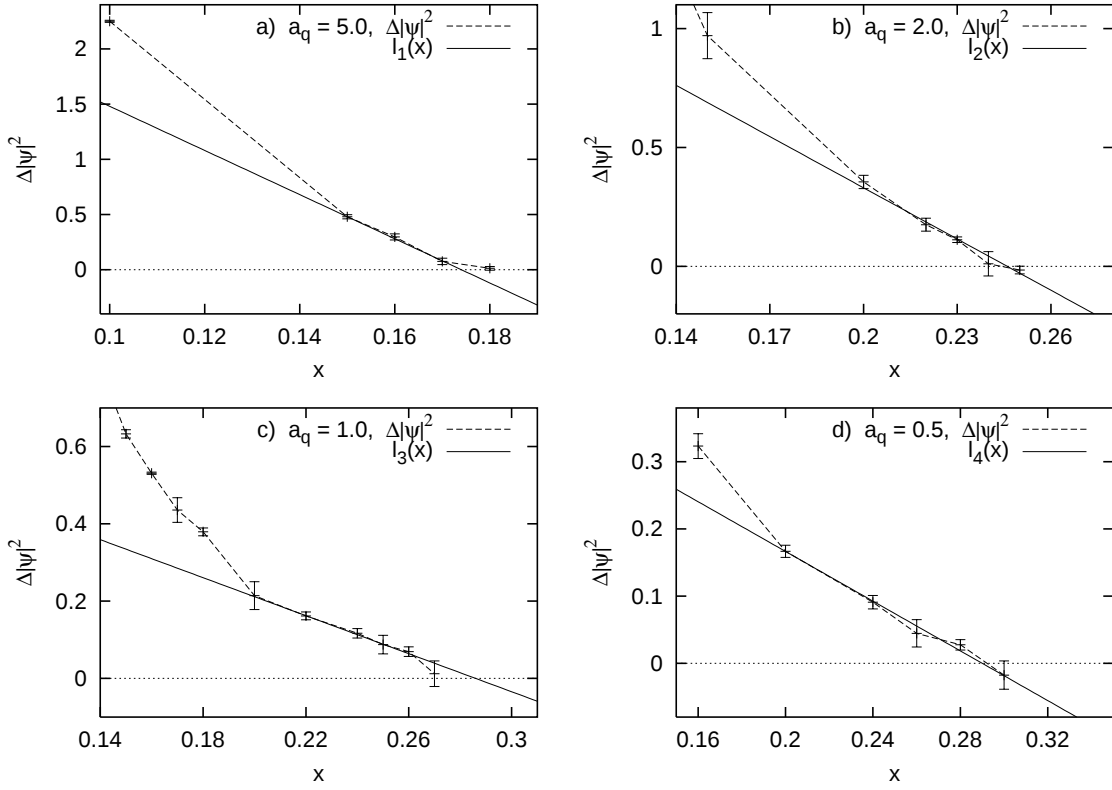


FIG. 3: $\lim_{N \rightarrow \infty} \overline{\Delta|\psi|^2}$ as a function of $x = \kappa^2$ for the lattice constants a) $a_q = 5.0$, b) $a_q = 2.0$, c) $a_q = 1.0$, d) $a_q = 0.5$. The line $l_i(x)$, $i = 1, \dots, 4$ is a fit to Eq. 5 where x_c is given in Table II.

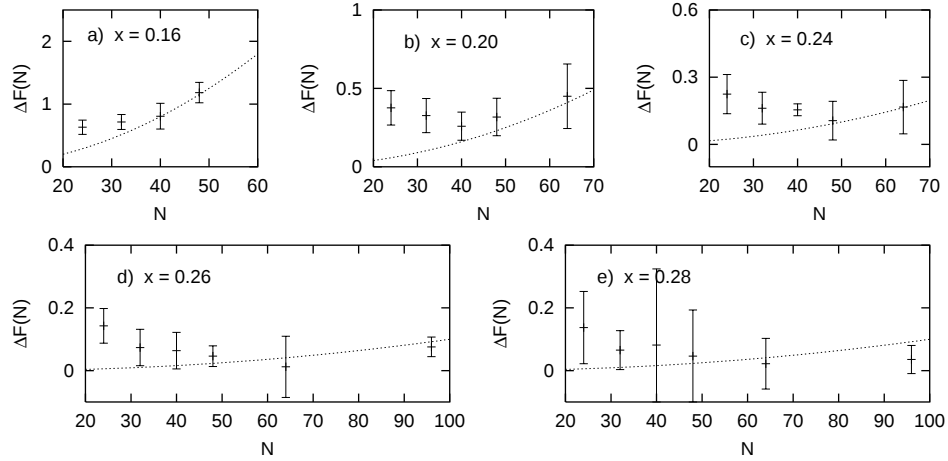


FIG. 4: $\Delta F(N) = \ln P_{\max}(N) - \ln P_{\min}(N)$ for $a_q = 0.5$. The line is $\propto N^2$ which is the scaling in Eq. 3 (for $d = 3$).

same lattice size in lattice units. The size of N necessary to access the scaling regime is (approximately) inversely proportional to the lattice constant a_q .

In Fig. 5, we show $x_{\text{tri}}(a_q)$ found from extrapolation of $\overline{\Delta|\psi|^2}$ to zero and from finite size scaling of $\Delta F(N)$ as given in Table II. A linear fit to the data gives $\lim_{a_q \rightarrow 0} x_{\text{tri}}(a_q) = 0.287 \pm 0.004$ with a confidence level of 25%. This is probably an underestimate of the error,

since we have no particular reason to assume a linear behavior. Since the errors in $x_{\text{tri}}(a_q)$ increases considerably when we reduce a_q one cannot rule out other behaviors, as quadratic. From the “worst case scenario” shown by the dotted lines in the figure we get $\lim_{a_q \rightarrow 0} x_{\text{tri}}(a_q) = 0.295 \pm 0.025$. This in all likelihood gives a more realistic estimate of the error, and we therefore give our final estimate of κ_{tri} as $\lim_{a_q \rightarrow 0} \kappa_{\text{tri}}(a_q) = (0.76 \pm 0.04)/\sqrt{2}$.

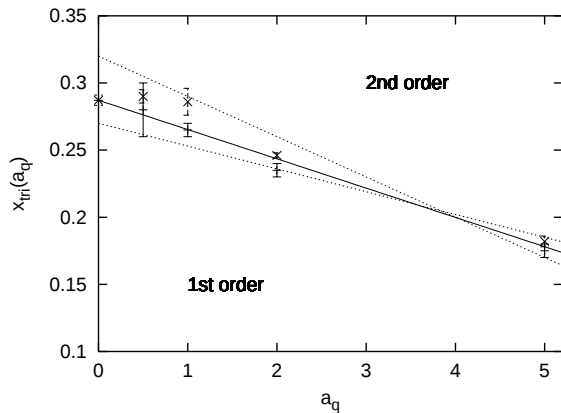


FIG. 5: Plot of $x_{\text{tri}}(a_q)$ using the results from extrapolation of $\Delta|\psi|^2$ to zero and from finite size scaling of $\Delta F(N)$ given in Table II. The solid line is a linear fit giving $\lim_{a_q \rightarrow 0} x_{\text{tri}}(a_q) = 0.287 \pm 0.004$. The dotted lines indicate “worst case scenarios” giving $\lim_{a_q \rightarrow 0} x_{\text{tri}}(a_q) = 0.295 \pm 0.025$.

VII. CONCLUSION

In summary, we have presented results from large scale Monte Carlo simulations showing that the critical value of the Ginzburg-Landau parameter that separates first order from second order behavior at the superconductor-normal metal transition point, is $\kappa_{\text{tri}} = (0.76 \pm 0.04)/\sqrt{2}$. This is in remarkable agreement with the first estimate of κ_{tri} obtained by Kleinert¹⁴ using a mean-field theory on the dual of the Ginzburg-Landau model, but differs almost by a factor of two from the subsequent early simulation results of Bartholomew.¹⁶

The reason for the remarkable agreement with our result and those of Ref. 14, is that for small to intermediate values of κ , the original problem is in the strong coupling

regime and is mapped onto a weak-coupling problem in the dual formulation. The dual model is then expected to yield rather precise results at the mean-field level.¹⁴ The dual description of the Ginzburg Landau model has recently met with considerable success in predicting the phase-structure of extreme type-II superconductors, even in magnetic fields.^{31,32,33,34} We interpret the good agreement between our results and those of Ref. 14 as further support to the dual description of the Ginzburg-Landau model, now also in the intermediate- κ region.

We have also argued that this κ_{tri} coincides with the κ separating type-I and type-II superconductivity. In the superconducting regime for $\kappa \in (\kappa_{\text{tri}}, 1/\sqrt{2})$ we thus predict the possibility of going from type-I to type-II superconductivity by increasing the temperature. This could in principle be possible to observe by studying the vortex structure of a superconductor with such intermediate values of κ by small-angle neutron scattering, when lowering the temperature through the line $x_c(y)$. However, more work is needed to elucidate the properties of the line $x_c(y)$ in Fig. 1.

Acknowledgments

We especially thank Dr. K. Rummukainen for generously providing us with the software for the data analysis, and for numerous helpful discussions during a visit by two of us (S.M. and J.H.) to Nordita, and later. We also thank Prof. H. Kleinert, Dr. F. Nogueira, and Prof. Z. Tešanović for useful discussions. We also thank all of the above for critical readings of the manuscript. A. S. thanks H. Kleinert and the Freie Universität Berlin for their hospitality while this work was being completed. This work was supported by the Norwegian Research Council via the High Performance Computing Program and Grant No. 124106/410 (S.M. and A.S.), and by NTNU through a fellowship (J.H.).

-
- * Electronic address: Sjur.Mo@phys.ntnu.no
 † Electronic address: Joakim.Hove@phys.ntnu.no
 ‡ Electronic address: Asle.Sudbo@phys.ntnu.no
¹ S. Coleman and E. Weinberg, Phys. Rev. D **7**, 1888 (1973).
² P. G. deGennes, Solid State Commun. **10**, 753 (1972).
³ T. C. Lubensky and J.-H. Chen, Phys. Rev. B **17**, 366 (1978).
⁴ H. Kleinert, *Gauge fields in condensed matter. Vol. 2: Stresses and defects. Differential geometry, crystal melting* (Singapore: World Scientific, 1989).
⁵ X. G. Wen and Y. S. Wu, Phys. Rev. Lett. **70**, 1501 (1993).
⁶ L. Pryadko and S. C. Zhang, Phys. Rev. Lett. **73**, 3282 (1994).
⁷ A. Vilenkin and E. P. S. Shellard, *Cosmic strings and other topological defects* (Cambridge University Press, 1994).
⁸ M. Tinkham, *Introduction to Superconductivity* (McGraw-Hill, 1996), 2nd ed.
⁹ B. I. Halperin, T. C. Lubensky, and S. K. Ma, Phys. Rev. Lett. **32**, 292 (1974).
¹⁰ K. Kajantie, M. Karjalainen, M. Laine, and J. Peisa, Nucl.

- Phys. B **520**, 345 (1998), hep-lat/9711048.
¹¹ B. I. Halperin and T. C. Lubensky, Solid State Communications **14**, 997 (1974).
¹² C. W. Garland and G. Nounesis, Phys. Rev. E **49**, 2964 (1994).
¹³ C. Dasgupta and B. I. Halperin, Phys. Rev. Lett. **47**, 1556 (1981).
¹⁴ H. Kleinert, Lett. Nuovo Cim. **35**, 405 (1982).
¹⁵ H. Kleinert, *Gauge fields in condensed matter. Vol. 1: Superflow and vortex lines. Disorder fields, phase transitions* (Singapore: World Scientific, 1989).
¹⁶ J. Bartholomew, Phys. Rev. B **28**, 5378 (1983).
¹⁷ K. Kajantie, M. Karjalainen, M. Laine, and J. Peisa, Phys. Rev. B **57**, 3011 (1998), cond-mat/9704056.
¹⁸ S. Kolnberger and R. Folk, Phys. Rev. B **41**, 4083 (1990).
¹⁹ R. Folk and Y. Holovatch, in *Correlations, Coherence, and Order*, edited by D. V. Shopova and D. I. Uzunov (Kluwer Academic/Plenum Publishers, N.Y. - London, 1999), pp. 83–116, cond-mat/9807421.
²⁰ S. Elitzur, Phys. Rev. D **12**, 3978 (1975).

- ²¹ K. Kajantie, M. Laine, T. Neuhaus, J. Peisa, A. Rajantie, and K. Rummukainen, Nucl. Phys. B **546**, 351 (1999), hep-ph/9809334.
- ²² J. Lee and J. M. Kosterlitz, Phys. Rev. Lett. **65**, 137 (1990).
- ²³ I. D. Lawrie and S. Sarbarch, in *Phase Transitions and critical phenomena*, edited by C. Domb and J. L. Lebovitz (Academic Press, London, 1984), vol. 9, pp. 1–161.
- ²⁴ J. Hove, S. Mo, and A. Sudbø, Phys. Rev. Lett. **85**, 2368 (2000), cond-mat/0008112.
- ²⁵ M. Laine, Nucl. Phys. B **451**, 484 (1995), hep-lat/9504001.
- ²⁶ M. Laine and A. Rajantie, Nucl. Phys. B **513**, 471 (1998), hep-lat/9705003.
- ²⁷ P. Dimopoulos, K. Farakos, and G. Koutsoumbas, Eur. Phys. J. C **16**, 489 (2000), hep-lat/9911012.
- ²⁸ K. Kajantie, M. Laine, K. Rummukainen, and M. Shaposhnikov, Nucl. Phys. B **466**, 189 (1996), hep-lat/9510020.
- ²⁹ A. M. Ferrenberg and R. H. Swendsen, Phys. Rev. Lett. **61**, 2635 (1988).
- ³⁰ A. M. Ferrenberg and R. H. Swendsen, Phys. Rev. Lett. **63**, 1195 (1989).
- ³¹ Z. Tešanović, Phys. Rev. B **59**, 6449 (1999).
- ³² A. K. Nguyen and A. Sudbø, Europhysics Letters **46**, 780 (1999), cond-mat/9811149.
- ³³ A. K. Nguyen and A. Sudbø, Phys. Rev. B **60**, 15307 (1999), cond-mat/9907385.
- ³⁴ J. Hove and A. Sudbø, Phys. Rev. Lett. **84**, 3426 (2000), cond-mat/0002197.
- ³⁵ The fine structure constant is given by $\alpha_s = \frac{\mu_0 c e^* 2}{4\pi\hbar}$ where $2e^*$ is the *effective* charge of a Cooper pair.
- ³⁶ We acknowledge Prof. H. Kleinert for pointing out this formula to us.
- ³⁷ In perturbation theory it is *necessary* to fix a gauge to avoid infinities from the infinite number of physically equivalent configurations. For simulations only the explicitly sampled configurations contribute, and no infinities arise. Finally the implementation on a parallel computer is simplest without gauge fixing.
- ³⁸ The proportionality factor between ΔF and the cross-sectional area L^{d-1} is the surface tension σ , which vanishes at x_{tri} , but due to the difficulty in getting proper L^{d-1} scaling of ΔF , we have not considered σ .
- ³⁹ Indeed, it has been customary to describe as “tricritical” any point at which a continuous transition becomes discontinuous, irrespective of the number of phases which coexist along the first-order line or of the number of lines or surfaces of ordinary critical points which, in a suitably enlarged parameter space, may be found to meet here.
- ⁴⁰ Note that in the London limit, with spatially constant amplitude, one cannot access the type-I regime. The 3DXY model coupled to a gauge-field is the dual of the 3DXY-model with no gauge-field fluctuations. The latter has a critical point corresponding to the 3DXY universality class, while the former recently has been shown explicitly to have a stable infrared charged fixed point. See J. Hove and A. Sudbø, Phys. Rev. Lett., **84**, 3426 (2000).
- ⁴¹ We have used equal *height* histograms instead of equal *weight*. The reason for this is that, in particular for small systems, the histograms are quite asymmetric. Then the equal weight histograms are not well defined for weak first order transitions. Both methods should give the same results in the infinite volume limit, but the convergence rate may be different.
- ⁴² In addition to $|\psi|^2$ we have also studied other quantities, in particular

$$\bar{L} = \frac{1}{3N^3} \sum_{\mathbf{x}, i} \cos(\arg[\psi^*(\vec{x})U_i(\vec{x})\psi(\vec{x} + \hat{i})]),$$

which varies between zero in the symmetric state and one in the broken state, quite similar to the more familiar 3DXY quantity $\langle \cos(\theta(\mathbf{x}) - \theta(\mathbf{x} + \hat{i})) \rangle$. However, the general picture is that the different observables give essentially the same information, and we have therefore focused mainly on Eq. 11, which has a well defined continuum limit.